

Full Length Research Paper

Deterioration and corrosion in scoria based blended cement concrete subjected to mixed sulfate environment

Khandaker M. Anwar Hossain

Department of Civil Engineering, Ryerson University 350 Victoria Street, Toronto, Ontario, M5B 2K3, Canada. E-mail: ahossain@ryerson.ca

Accepted 17 October, 2006

The use of blended cements incorporating supplementary cementing materials and cements with low C_3A content is becoming common to prevent the deterioration of concrete structures subjected to aggressive environments. This paper presents the results of an investigation on the performance of finely ground volcanic scoria (VS) based ASTM Type I and Type V (low C_3A) blended cement concrete mixtures with varying immersion period of up to 48 months in environments characterized by the presence of mixed magnesium-sodium sulfates. The concrete mixtures comprise a combination of two Portland cements (Type I and Type V) and two VS based blended cements with two water-to-binder ratio of 0.35 and 0.45. Background experiments (in addition to strength and fresh properties) including X-ray diffraction (XRD), Differential scanning calorimetry (DSC), mercury intrusion porosimetry (MIP) and rapid chloride permeability (RCP) were conducted on all concrete mixtures to determine phase composition, pozzolanic activity, porosity and chloride ion resistance. Deterioration of concrete due to mixed sulfate attack and corrosion of reinforcing steel were evaluated by assessing concrete weight loss and measuring corrosion potentials and polarization resistance at periodic intervals throughout the immersion period of 48 months. Plain (Type I/V) cement concretes, irrespective of their C_3A content performed better in terms of deterioration and corrosion resistance compared to Type I/V VS based blended cement concrete mixtures in mixed sulfate environment.

Keywords: volcanic scoria, sulfate attack, blended cement concrete, corrosion/deterioration

INTRODUCTION

The presence of sulfate ion causes deterioration of concrete structural components exposed to marine environments or placed in soils and groundwater contaminated with sulfate salts. Research on concrete deterioration due to the presence of sulfate ions had been continued for decades. Sulfate attack on concrete is a complex process and many factors such as cement type, sulfate cation type, sulfate concentration and exposure period may affect the sulfate resistance (Neville, 2004; Cohen and Mather, 1991). The sulfate ions react with C_3A and $Ca(OH)_2$, to produce expansive and/or softening types of deterioration. The sulfate attack in marine environment gives rise to expansive ettringite, gypsum, and brucite and sometimes is associated with calcite formation (Mehta, 1973; Frigione and Sersale, 1989).

The sulfate resistance of concrete structures can be improved by controlling sulfate permeation into concrete and the sulfate attack can be prevented either by chang-

ing cement from ASTM Type I to Type II or Type V or by introducing pozzolans such as fly ash, blast furnace slag and finely ground volcanic scoria (VS) in concrete (Hossain, 2004; Kalousek et al., 1972; Al-Amoudi et al., 1994; Wong and Poole, 1987).

ASTM Type V cement, with a low C_3A , is recommended in structures placed in such environment. Typically, ASTM Type I cement contains between 8 and 12% C_3A , whereas Type II cement contains less than 8% C_3A and Type V cement less than 5% C_3A . Significant development in cement chemistry over the past two decades, resulted in cements with a high C_3S/C_2S content (Rasheduzzafar, 1990). This increase in C_3S/C_2S ratio results in increased calcium hydroxide content in the hardened cement concrete, thereby enhancing the susceptibility of such cements to softening type of sulfate attack (Rasheduzzafar, 1990; ACI Committee, 1991). Irassar et al. (2000) reported that a low C_3S/C_2S ratio is a significant

positive factor in the choice of cement for good sulfate resistance. The sulfate permeation can also be controlled by: increasing compactness, lowering water-to-cement ratio, proper curing, surface treatment, and use of precast concrete in place of cast-in-situ concrete (ACI Committee, 1991).

It is reported that the limitation on C_3A content is not the ultimate answer to the problem of sulfate attack (Kalousek et al., 1972; Rasheeduzzafar, 1990; Lawrence, 1990). Mehta (1993) pointed out that Type V cement addresses only the problem of sulfate expansion associated with the ettringite formation. Therefore, Type V cement can be particularly efficacious when calcium sulfate is the attacking medium, although it could be beneficial with respect to the prevention of the formation of gypsum owing to the action of sodium sulfate. Thus, Type V cement is of no avail in the attack of calcium hydroxide and C-S-H and the subsequent loss of strength (Mehta, 1993).

The use of blended cement made with supplementary cementitious materials (such as: fly ash, silica fume, and blast furnace slag) is, therefore recommended in sulfate environments (Frigione and Sersale, 1989; Al-Amoudi et al., 1994). The sulfate resistance of such blended cement concretes depends on the composition and physical properties of concrete as well as type and concentration of sulfate ion. The improvement in sulfate resistance for fly ash and silica fume based blended cement concretes is reported. This is attributed to the pore refining and pore refinement effect occurring due to pozzolanic reaction where calcium hydroxide becomes bound by fly ash or silica fume converting it into secondary C-S-H gel. However, with additional cementitious materials, the complexity of sulfate attack becomes even greater. Taylor (1999) pointed out that if slag has low alumina content, it improves the sulfate resistance, but with a high content of alumina, the reverse is the case.

Young et al. (1998) report that sulfate attack can be prevented by any one of three factors: low w/c, low calcium hydroxide content, or low C_3A content. If their claim is valid, then adequate protection of concrete should be ensured by the use of a low w/c alone or by the use of Type V cement alone. Neville (2004) believed that these solutions are too sweeping and not valid under all circumstances. Al-Amoudi (2002) reported that lowering w/c has a deleterious effect on the resistance of concrete exposed to magnesium sulfate, the use of Type V cement being of no avail. A likely explanation is that at low values of w/c, there is limited pore space to accommodate the products of reactions with sulfate, namely, magnesium silicate hydrate (which has no adhesive properties) and gypsum.

Although significant progress has been made on the understanding of the mechanism of sulfate attack in concrete, our knowledge and understanding remains inadequate (Neville, 2004). Still the role of C_3A , cement content, water to binder ratio, and the role of pozzolanic mat-

erials remain controversial.

Lightweight VS is abundant in various parts of the world including Turkey, Papua New Guinea (PNG) and Saudi Arabia (Hossain, 2004). VS is pyroclastic ejecta, irregular in form and generally very vesicular and has the basic composition of basalt. VS can be utilized in several industrial applications including the manufacturing of lightweight concrete, as a source of pozzolan to manufacture blended cement, as a heat insulating material, in addition to other uses such as fillers, filter materials, absorbents and other architectural applications. Research had been conducted over the last few years on the use of lightweight volcanic scoria (VS) in cement and concrete production (Hossain, 2004; Hossain, 2006). Research suggested the manufacture of blended Portland volcanic scoria cement (PVSC) with maximum cement replacement of up to 20% (Hossain, 2006).

Durability of concrete is one of its most important properties and it is essential that the concrete made with VS based blended cements should be capable of preserving its durability throughout the life of structures. ACI 318-813-1999 and BS 8110-1985 and other codes of practices provide guidelines on the quality of concrete and the type of cement to be used for varying sulfate concentrations. However, these guidelines do not specifically cover the sulfate resistance of VS based blended cement concrete. Until recently, little research had been conducted on the performance of VS based blended cements subjected to such aggressive environments. Moreover, no data is available on concrete deterioration and corrosion of rebars in VS based blended cement concretes when exposed to sulfate-bearing environments.

Previous studies on sulfate attack are conducted mainly by using sodium, magnesium and calcium sulfate solutions (Neville, 2004; Lawrence, 1990). However, due to limited solubility of calcium sulfate in water at normal temperatures (about 1400 mg/l SO_4), higher concentrations of sulfate ions in ground waters are generally due to the presence of magnesium and sodium sulfates. Both of these salts are abundant in many parts of the world including Arabian Gulf coast (known as saline sabkha soils) and coastal areas of Papua New Guinea. It is important to study the performance of concretes in such mixed sulfate environment.

This paper presents the results of the research conducted to assess deterioration and corrosion resistance of concrete mixtures, which comprised a combination of two Portland cements (Type I and Type V) and two VS based blended cements with Type I/V cements having two water-to-binder ratios, exposed to mixed sulfate solution for a period of 48 months. Such a study is of significant practical interest and can be helpful in the selection of VS based blended cements for structures subjected to mixed sulfate environments characterized by the presence of magnesium as exists in many parts of the world.

Table 1. Comparative study of chemical and physical properties of VS and cement

	VS	ASTM Type I cement	ASTM Type V cement
Chemical properties			
Chemical Compounds	Mass, %	Mass, %	Mass, %
Calcium oxide (CaO)	5-8	64.1	65.0
Silica (SiO ₂)	45-50	21.4	21.9
Alumina (Al ₂ O ₃)	13-15	5.7	3.2
Iron oxide: Fe ₂ O ₃	3-4	3.5	3.9
FeO	4-6		
Sulphur trioxide (SO ₃)	0.01-0.02	2.1	2.5
Magnesia (MgO)	4-6	2.1	2.2
Sodium oxide (Na ₂ O)		0.5	0.2
Potassium oxide (K ₂ O)	4-6	0.5	0.3
Loss on ignition	1.25-1.50	1.1	0.8
Free lime (CaO)	-	0.7	0.6
Physical properties			
Fineness, m ² /kg	290	320	373
Sp. gravity	2.15	3150	3150

Table 2. Potential phase composition of the cementing materials from X-ray diffraction

Phase	Plain cements		VS based blended cements	
	Type I	Type V	PVSC (20% VS) Type I	PVSC (20% VS) Type V
C ₃ S	68.1	71.2	55.6	58.6
C ₂ S	14.1	10.5	9.1	6.9
C ₃ A	8.1	3.5	5.3	1.8
C ₄ AF	9.2	11.1	6.9	7.1
Other	2.4	2.9	7.6	8.1
Total	99.7	99.2	84.5	82.5
Glassy fraction*	0.3	0.8	15.5	17.5

* obtained by difference

EXPERIMENTS

Materials

Volcanic scoria (VS) used in this investigation was collected from a quarry near the town of Goroka in the highland province of Papua New Guinea. VS samples collected from the source were grounded to fine powder using a ring crusher to obtain a Blaine fineness of about 295 m²/kg (Table 1). ASTM C 150 Type I and Type V cements were used as plain cements as well as to manufacture blended cements. Chemical and physical properties of VS are compared with those of cements in Table 1. Chemical analysis indicates that VS is principally composed of silica (45-50%); while the main oxide component of PC is calcium oxide (60-67%). However, VS also has calcium oxide, alumina and iron oxide (25-33%). The total oxide content of sodium and potassium known as 'alkalis' is found to be higher in scoria (4-6%) than in PC (1% maximum). Ground scoria with a specific gravity of 2.15 was also lighter than PC.

Production of scoria based blended cements

Blended cements were produced in the laboratory by thoroughly mixing cement and VS using a heavy duty paddle mixer. Blended cements were prepared by replacing 20% of Type I and Type V cements with VS. Quantitative X-ray diffraction (XRD) analysis of Type I, Type V cements as well as blended cements with 20% VS (PVSC) as cement replacement, provided valuable information on the phase composition of these materials (Table 2).

Concrete mix proportions

ASTM Type I and Type V plain as well as VS based blended (with 20% VS) cements were used in the preparation of concrete mixes. The fine and coarse aggregates were local natural river sand and 20-mm maximum size crushed limestone respectively. The particle size distributions as per ASTM C 136-01 for aggregates are presented in Table 3. The bulk density and water absorption of aggregates are also presented in Table 3. Table 4 shows the details of mix pro-

Table 3. Grain size distribution and properties of aggregates

Grain size distribution of aggregates			Physical properties aggregates			
Sieve Size, mm	Fine % passing	Coarse % passing		Bulk density (kg/m ³)		Water absorption (%)
				Oven dry	SSD	
20	100	100	Coarse	2570	2640	2.49
12.7	100	71	Fine	2610	2660	0.60
9.5	100	28				
4.75	93	0				
2.36	70.5					
1.18	51.5					
0.6	35					
0.3	20.5					
0.15	8.5					

Table 4. Mix proportions and fresh and strength properties of concrete mixtures

Mix ID	VS (%)	W/B	Materials (kg/m ³)				Slump mm	Air content %
			W	C	Aggregates			
					Fine	Coarse		
Series A: W/B = 0.45								
AType I	0	0.45	180	400	770	1020	80	2.5
AType V	0	0.45	180	400	770	1020	82	2.5
A20VS-I	20	0.45	180	320	740	1019	83	3.1
A20VS-V	20	0.45	180	320	740	1019	84	3.2
Series B: W/B = 0.35								
BType I	0	0.35	140	400	800	1080	80	2.2
BType V	0	0.35	140	400	800	1080	81	2.3
B20VS-I	20	0.35	140	320	765	1080	84	2.9
B20VS-V	20	0.35	140	320	765	1080	84	2.8

C: Cement W: Water B: Binder

portions of 8 different concrete mixtures classified into series A and B. First letter in mix designation represents the series, numeric before VS represents % of VS and roman letter at the end represents type of cement. Two different water-to-binder ratios (W/B) of 0.35 (for series B) and 0.45 (for Series A) were used while the total binder content was kept constant at 400 kg/m³. A naphtha-alene sulphonate-based superplasticizer was used at a dosage of 1% (solid mass) by weight of binder in concrete mixtures (series B) made with a W/B of 0.35.

Investigation on fresh, mechanical and durability characteristics

Tests were conducted to evaluate fresh and hardened properties such as slump, air content, compressive strength and density of eight concrete mixtures with Type I/Type V plain and VS based blended cements. In addition, durability and micro-structural characteristics of concrete mixtures were evaluated through rapid chloride permeability (RCP), mercury intrusion porosimetry (MIP) and differential scanning calorimetry (DSC).

The slump of fresh concrete mixtures was determined as per ASTM C 143-00 while the air content was determined by pressure meter as per ASTM C 231-97. 150 x 300-mm (for compressive strength) and 100 x 200-mm cylinder (for RCP, MIP and DSC) specimens were cast. Specimens were removed from the moulds

(wrapped in wet jute bags) after 24 h of casting and then placed in a water tank at 23 ± 2 °C. After 28, days of water curing compressive strength test was performed on 150 x 300-mm cylinders as per ASTM C-39.

100 x 200-mm cylinders were transferred to a relative humidity room maintained at 23 ± 2 °C and 50 ± 5 percent relative humidity and kept there for further 4 weeks until testing at 56 days. At 56-day, RCP test was conducted as per ASTM C 1202-97 on 100 x 50-mm concrete slices to determine resistance to chloride ion penetration. This test determines the electrical conductance of concrete to provide a rapid indication of its resistance to the penetration of chloride ions. The chloride ion resistance of concrete gives an indirect measure of its permeability and internal pore structure, as more current passes through a more permeable concrete. The porosity and pore size distribution were measured using MIP, which had a measuring pressure ranging from 0.01 to 200 MPa. The contact angle selected was 140° and the measurable pore size ranged from 0.004 to 144 µm. The Washburn equation was used to calculate the pore radii (Washburn, 1921). The samples in the form of pellets of about 5 mm in size, consisted of hardened cement mortar, were collected from the crushed concrete cylinders at 56-day and immediately soaked in acetone to stop the further hydration. The samples were dried in an oven at 60°C for 48 h before testing.

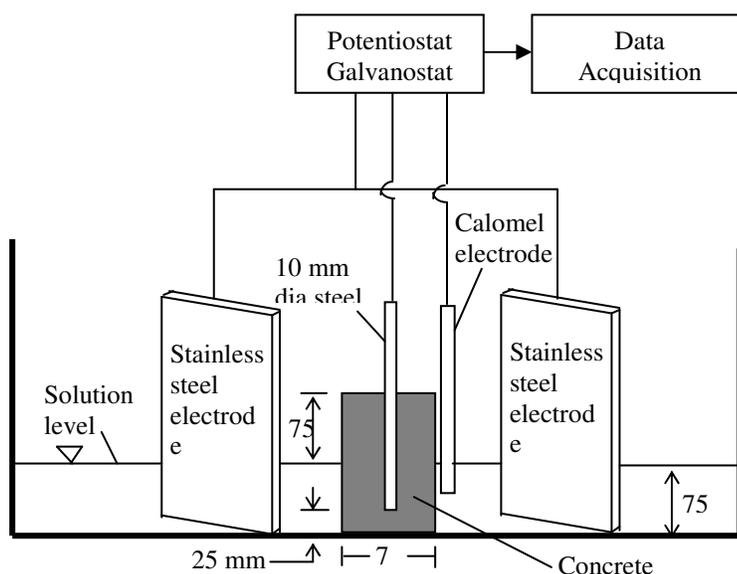


Figure 1. Experimental set-up for polarization resistance measurements showing a specimen

The DSC test was performed on the hardened mortar samples taken from the crushed concrete cylinders after 56 days of curing to determine the quantity of Ca(OH)_2 formed in the mortars. The samples used weighed around 60 mg. The samples were heated at a constant heating rate of 10°C per minute to $1100\text{--}1200^\circ\text{C}$, in a dynamic helium atmosphere. The DSC data analysis gave graphs of heat flow between the sample and reference crucibles vs. temperature. DSC thermograms showed peaks due to endothermic (heat absorbing) and exothermic (heat releasing) reactions. The Ca(OH)_2 content was equivalent to the area (enthalpy) under the respective endothermic peaks. The endothermic peak for Ca(OH)_2 was observed at around 450°C . The size of the area under the curve was related to the quantity of the material in the sample. At least two DSC analyses were performed for each concrete.

Investigation on concrete exposed to sulfate bearing environment

Details of specimens

75 mm in diameter and 150 mm in height concrete cylinders with a centrally placed 10 mm diameter reinforcing bar (Figure 1) were used to study the effect of the sulfate environment on the electrochemical behavior of embedded reinforcements in Type I/V plain and Type I/V VS based concrete mixtures. The steel bars embedded in concrete were coated with an epoxy paint at the concrete-air interface and at their ends to prevent crevice corrosion. The reinforcing bars were cleaned thoroughly using silicon carbide paper and degreased before casting in concrete. The steel bar had an effective cover of 25 mm at the bottom.

100 x 100-mm concrete cubes were used to study the effect of the sulfate environment on the physico-chemical characteristics of Type I/V plain and Type I/V VS based concrete mixtures.

Casting and curing of specimens

The concrete constituents were mixed in a revolving-drum type mixer for four minutes. After casting, the specimens were wrapped

in wet jute bags for curing for 24 h prior to demoulding. After demoulding, specimens were cured for 28 days in potable water in a tank where the ratio of the volume of curing water to the volume of specimens was kept low (around 0.48). A higher ratio would allow much of the cement alkali and perhaps some of the VS alkali to leach out of the concrete. This would seriously influence the subsequent corrosion measurement as loss of the alkali would reduce the margin of the hydroxide ion concentration needed for passivation especially in the presence of chloride. After 28 days of water curing, the cube specimens were air-dried for one day in the laboratory ($23 \pm 2^\circ\text{C}$) and their initial weight (W_i) were recorded.

Test solutions and specimen immersion schemes

The cube and cylinder specimens were exposed to mixed sulfate environment by immersing in test solutions in two separate tanks. Two separate exposure tanks were needed to submerge cylinder specimens at a specific height and to fully submerge cube specimens. In this study, the concentration of the test solution was 2.1% SO_4^{2-} (21,000 mg/l) where sodium sulfate and magnesium sulfate (proportioned to provide 50% of the sulfate concentration from each of the two salts) were used to provide sulfate ions. The above exposure condition represents very severe sulfate exposure condition according to ACI 318-99. However, this concentration is prevalent in many parts of the world especially saline soils in Arabian Gulf coast and coastal areas of Papua New Guinea (Al-Amoudi et al., 1992). The level of the solution was adjusted so that half the depth of the cylinder specimens with embedded steel was in the solution at all times (Figure 1). Cube specimens were exposed to test solution in fully submerged condition for assessing physical deterioration. The solutions in both tanks were periodically agitated and their concentrations were monitored and adjusted each month.

Assessments of physico-chemical deterioration

The physical deterioration due to sulfate attack was evaluated in terms of the reduction/increase in weight of the specimens after 6, 12, 18, 24, 30, 36 and 48 months of immersion. The specimens

were retrieved, air-dried for one day in the laboratory environment, cleaned gently with a towel to remove loose particles and weighed. The weight loss of the concrete materials (L) was determined using Eq. 1:

$$L = \frac{W_i - W_t}{W_i} \times 100$$

Eq. 1

where W_i = average initial weight of three specimens (g) and W_t = average weight of three specimens after an exposure of t months (g).

The DSC test was performed on mortar samples taken from cubes exposed to sulfate environment for 48 months to determine the quantity of $\text{Ca}(\text{OH})_2$ following the procedure as described before.

Assessments of electro-chemical behavior of embedded steel

The corrosion process of steel in concrete can be followed using several electrochemical techniques. Monitoring of open circuit potential (OCP) is the most typical procedure to the routine inspection of reinforced concrete structures (Broomfield et al., 1990) [32]. Its use and interpretation are described in the ASTM Standard Test Method for Half-Cell Potential of Reinforcing Steel in Concrete (ASTM C 876-1999). Measurement of d.c. polarization resistance with ohmic drop compensation has been applied since the 1970s and provides information about the corrosion rate (Montemor et al., 2000).

Corrosion activity in this study was monitored up to an immersion period of 48 months by measuring the corrosion potentials and polarization resistance at regular intervals. The corrosion potentials were measured using a high impedance voltmeter and noting the potentials against a saturated calomel electrode (SCE). Half-cell potentials more positive than -270 mV represent a passive state of corrosion while potentials more negative than -270 mV represent an active state of corrosion (ASTM C 876). The half-cell potential data collected using this technique gives a qualitative indication of the corrosion of reinforcing bars.

The linear polarization resistance technique was used to obtain quantitative information on the performance of concrete specimens in inhibiting reinforcing bar corrosion. The linear polarization resistance (R_p) was determined by running a polarization-resistance scan in the range of ± 10 mV of the corrosion potential using a potentiostat/galvanostat with IR compensation. A stainless steel frame placed outside the specimen was used as a counter-electrode, while a saturated calomel electrode was used as a reference electrode. Figure 1 shows the experimental set-up for the polarization resistance measurements. The Tafel constants were determined by running anodic and cathodic polarization scans. Current-interrupt technique was used to compensate for the internal-resistance (IR) drop between the concrete and the reinforcing bar.

Failure criterion due to sulfate attack

Concrete deterioration due to mixed magnesium-sodium sulfate environment is typically manifested by a progressive degradation leading to deterioration and weight loss and is also associated with increased softening and disintegration of the hardened cement matrix, characterized by non-cohesiveness and spalling of the surfaces. These features of binder decomposition akin to eating away of the hydrated cement paste leaving the aggregates exposed are best assessed by the weight loss of concrete materials as illustrated in this study. The strength reduction criterion is not applicable for the specimens used in this investigation while the length change

criterion is not suitable for this type of sulfate attack.

With regard to establishing a failure criterion based on weight loss, Cohen and Mather (1991) have reported that a loss of 5% (for beams) and 2.5% (for cubes) is to be adopted.

Failure criterion due to steel corrosion

ASTM C 876 criterion can be used to indicate whether the rebars were in an active state of corrosion or not, based on half-cell polarization resistance values. A threshold value of -270 mV SCE (based on saturated calomel electrode) can be used as per ASTM C 876.

The polarization resistance (PR) values can also be used to predict the time for initiation steel reinforcement corrosion for the embedded rebars in the various concrete mixtures via the use of Eq. 2.

$$C = A/PR \quad \text{Eq. 2}$$

where C = density of corrosion current in $\mu\text{A}\cdot\text{cm}^2$; $A = (\alpha_a * \alpha_c) / [2.3(\alpha_a + \alpha_c)]$; α_a and α_c = anodic and cathodic Tafel constants, respectively.

In absence of sufficient data on α_a and α_c for steel in concrete, a value of A equal to 26 in the active state of corrosion is frequently used (Andrade et al., 1986). Further, if current density (C) is greater than $0.3 \mu\text{A}\cdot\text{cm}^2$ (corresponding to a PR value of $87 \text{ k}\Omega\cdot\text{cm}^2$), the reinforcing steel will certainly be in an active state, and if C is less than $0.1 \mu\text{A}\cdot\text{cm}^2$ (corresponding to a PR value of $260 \text{ k}\Omega\cdot\text{cm}^2$), it is certainly passive (Andrade et al., 1986). It is therefore, logical to set the PR value of $87 \text{ k}\Omega\cdot\text{cm}^2$ as a threshold value for corrosion activation.

RESULTS

Fresh properties of VS based concrete mixtures



Table 4 presents the slump and air content of concrete mixtures. The slump of both series A and B concrete mixtures ranges between 80 and 84 mm. The air contents of Series A concrete mixtures ranges between 2.5 and 3.2% while those in Series B ranges between 2.2 and 2.9%. Increase in W/B increases the air content of Series A concrete mixtures compared to Series B. However, use of SP might also have a influence in the reduction of air content in Series B. Type of cements either Type I or Type V seems to have no influence on the fresh properties of concrete mixtures.

Strength, durability and micro-structural characteristics of concrete mixtures

Table 5 summaries strength and density (at 28-day) of concrete mixtures as well as test results of RCP, MIP and DSC tests conducted at 56-day. 28-day density of concrete mixtures ranges between 2366 and 2410 kg/m^3 . In general, findings can be summarized as: i) Type I/V VS based blended concrete showed lower strength, higher chloride ion resistance and lower porosity/average pore diameter than Type I/V plain concrete: this can be attributed to the fact that the strength gain of VS based pozzo-

Table 5. Strength, durability and micro-structural properties of concrete

Mix ID	28-day density kg/m ³	28-day compressive strength (MPa)	RCP (Coulombs)	Porosity (% v/v)	Avg. pore diameter (μm)	Ca(OH) ₂	
						Endothermic peak area J/g 56 days ⁺	48 months ⁺⁺
Series A: W/B = 0.45							
AType I	2401	38	2850	16.46	0.0464	105	75
AType V	2403	37	2805	16.39	0.0461	99	70
A20VS-I	2372	30	2330	15.55	0.0454	78	31
A20VS-V	2366	30	2325	15.45	0.0448	71	27
Series B: W/B = 0.35							
BType I	2410	49	2350	15.10	0.0432	102	74
BType V	2408	48	2306	15.03	0.0427	95	72
B20VS-I	2377	41	1990	13.70	0.0419	75	33
B20VS-V	2372	40	1970	13.60	0.0411	69	24
+ exposed to normal water curing ++ exposed to sulfate solution * not tested							

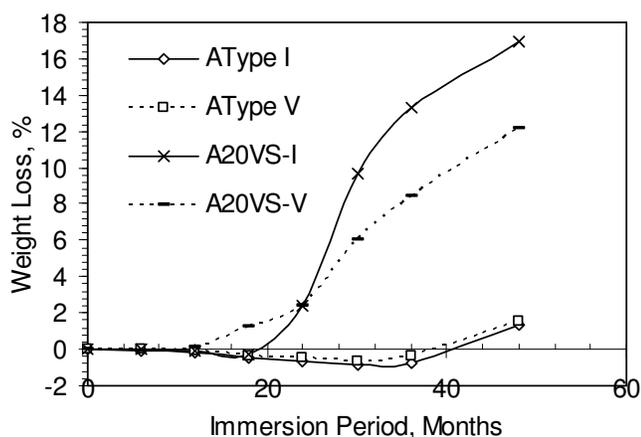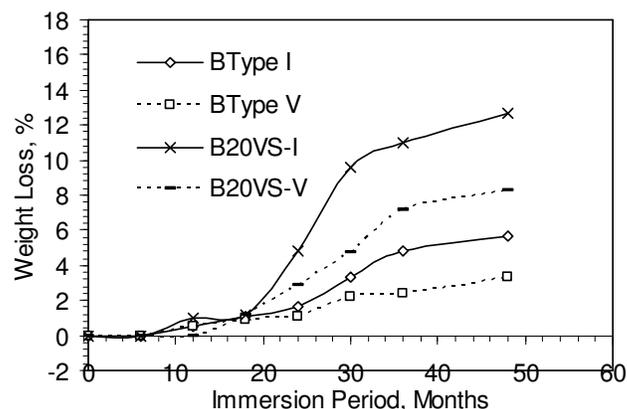**Figure 2.** Variation of weight loss with immersion period (Series A with W/B of 0.45)**Figure 3.** Variation of weight loss with immersion period (Series B with W/B of 0.35)

lanic concrete is not merely related to lowering of porosity, ii) concrete mixtures with higher W/B showed lower strength, lower chloride ion resistance and higher porosity/average pore diameter and iii) use of type V cements showed slightly better chloride ion resistance and lower porosity with no visible strength gain compared to Type I.

Upon hydration of cement, VS has the capability of partially obstructing voids and pores. This leads to a decrease of pore size and to a smaller effective diffusivity for either chloride or other species. DSC analysis mortars taken from crushed concrete (Table 5) reveals that the calcium hydroxide content of the VS-blended concrete is lower than that of the plain concrete. This indicates that the pozzolanic reactivity of VS consumes calcium hydroxide resulting from hydration of the cement. Such pozzolanic reaction of VS with calcium hydroxide, produces a denser concrete and thus inhibits the ingress of chloride ions. This can improve the chloride induced corrosion resistance of VS based concrete mixes compared to plain

concrete mixes. This is confirmed from lower porosity and higher chloride ion resistance of VS based concrete as observed in this study (Table 5). However, the mechanism of sulfate induced deterioration is different than chloride induced deterioration.

Concrete deterioration in mixed sulfate environment based on weight loss

The weight loss of various concrete specimens exposed to sulfate solution with immersion period is presented in Figures 2 and 3. Results exhibited initially a marginally negative weight loss/gain in weight which is more pronounced in Type I and Type V plain concrete mixtures in Series A with W/B of 0.45 (Figure 2). This phenomenon is attributable to the filling up of pores by the expansive reaction products, thereby densifying the hardened mortar mix and increasing the weight and strength (Montemor et al., 2000). Subsequently, the disruption of the hy-

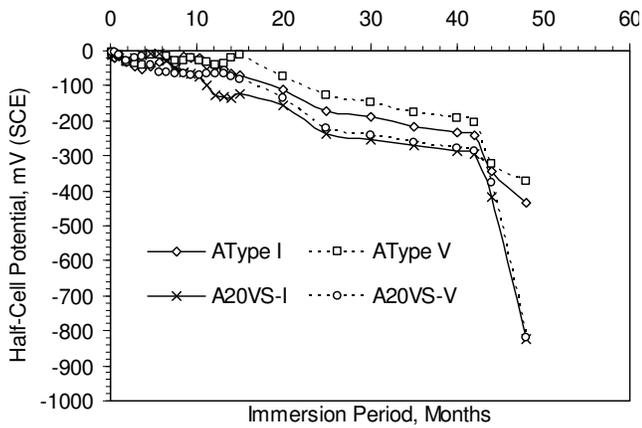


Figure 4. Variation of half-cell potential with immersion period (Series A)

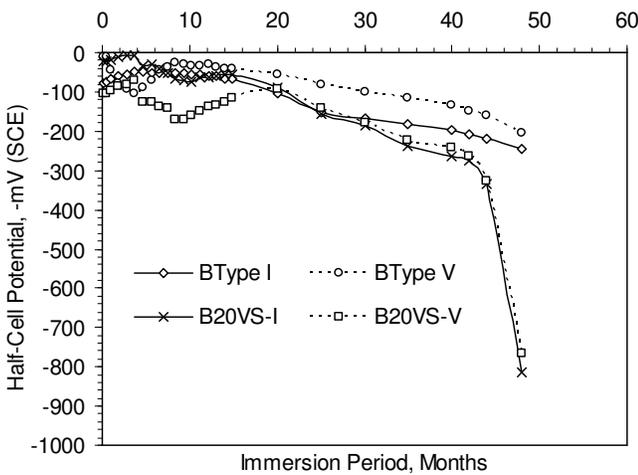


Figure 5. Variation of half-cell potential with immersion period (Series B)

drated cementitious matrix by these expansive reaction products resulted in a decrease in the weight of specimens, thus increasing the weight loss with immersion period. A decrease in W/B from 0.45 (Series A) to 0.35 (Series B) decreases the negative weight loss phenomenon (Figures 2 and 3).

Type I VS blended concrete mixes show an increase in weight loss after about 18 months compared with about 10 months for Type V VS blended concrete mixes and 40 months for Type I/V plain concrete mixes (Series A, Figure 2). The overall weight loss is higher in Type I VS blended concrete mixes compared to Type V VS blended concrete mixes and Type I/V plain concrete mixes. Type I/V plain concrete mixes showed the lowest weight loss compared with Type I/V VS concrete mixes (Figure 2: Series A). Type I and Type V plain concrete mixes in Series A showed similar weight loss throughout the immersion period of 48 months.

For Series B, weight loss increase seemed to be started earlier (within 10 months for all concrete mixes) than Series A mixes. Unlike in Series A, Type I plain concrete mixes showed higher weight loss compared to Type V plain concrete mixes in Series B (Figure 3). Similar to Series A, Type I VS blended concrete mixes showed higher weight loss compared to Type V VS based blended concrete mixes with the lowest weight loss observed in Type V plain concrete mixes.

VS based concrete mixtures in Series A and Series B showed similar weight loss throughout the immersion period.

Corrosion potentials

The corrosion potentials on steel in various concrete specimens are presented in Figures 4 and 5. These potential time curves were used to evaluate the time to initiation of rebar corrosion based on the ASTM C 876 criterion of -350 mV CSE (copper-sulfate electrode), corresponding to -270 mV SCE (saturated calomel electrode). No significant difference in half-cell potential is observed between Type I VS and Type V VS concrete mixtures. Type I/V plain concrete mixtures show less negative half-cell potential than Type I/V VS based concrete mixtures. The rate of increase in negative potential increased significantly (may be due to initiation of active state of corrosion in these mixtures) beyond an immersion period of 42 months for Type I/V VS based concrete mixtures. Figures 4 and 5 indicate that rebars embedded in all concrete mixtures, except Type I and V with W/B of 0.35 (Series B), exhibited more negative potential than the -270 mV SCE after 48 months of immersion. Therefore, the steel in these concrete specimens was in an active state of corrosion.

Polarization resistance



The variation of polarization resistance with immersion period in various concrete mixtures is presented in Figures 6 and 7. Initial polarization resistance on steel in various concrete mixtures was very high (ranging between 4993 and 5967 kΩ-cm² for Series A with W/B 0.45; between 3420 and 5512 kΩ-cm² for Series B with W/B 0.35). The polarization resistance decreased significantly (rate of decrease seems to be higher in Series A with W/B of 0.45 compared to Series B with W/B of 0.35) in an immersion period of 48 months.

DISCUSSION

Table 6 shows the variation in the performance of the 12 concrete mixtures in the magnesium-sodium sulfate test solutions after a long-term exposure period of 48 months

Table 6. Weight loss and corrosion data after 48 months of exposure

	Concrete weight loss (%)	Corrosion potential, SCE (-mV)	Polarization resistance (kOhm-cm ²)	Corrosion initiation (Months)
W/B =0.45				
Type I	1.34	-434	51	44
Type V	1.51	-372	69	44
20VS-I	16.9	-824	21	40
20VS-V	12.2	-819	8	40
W/B=0.35				
Type I	5.7	-245	630	no corrosion
Type V	3.3	-203	347	no corrosion
20VS-I	12.6	-815	24	42
20VS-V	8.3	-765	38	44

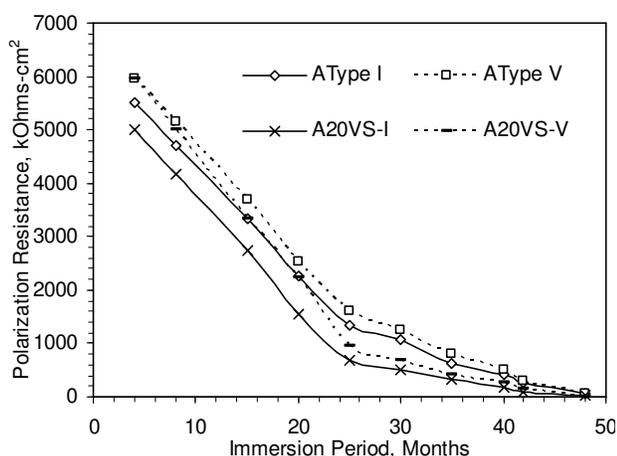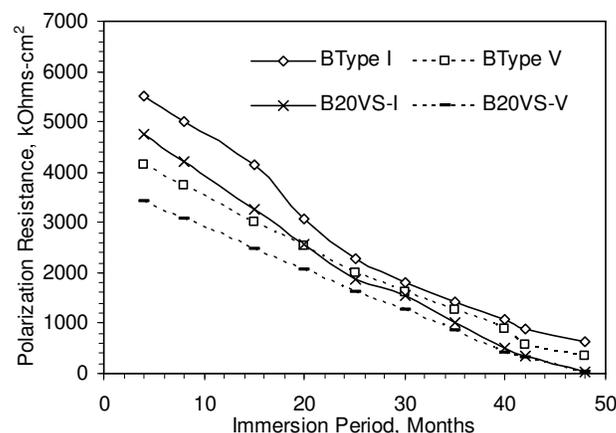**Figure 6.** Variation of polarization resistance with immersion period**Figure 7.** Variation of polarization resistance with immersion period

in terms of weight loss, corrosion potential and polarization resistance. Figure 8 shows typical deterioration of concrete samples after 48 months of exposure in magnesium-sodium sulfate solutions.

Influence of type of cement and C₃A content on sulfate attack

The 48 months polarization resistance did not clearly indicate the effect of type of cements (Type I or V) in plain and VS based concrete mixtures. However, based on 48 months corrosion potential data, Type V cements seems to show a slightly better performance in terms of corrosion resistance than Type I cements in both plain and blended cement concretes (Table 6). The 48 month weight loss of Type V plain and VS based concrete mixtures was generally lower compared to those of Type I VS based concrete mixtures with the exception of Type V having a W/B of 0.45 (Table 6).

Neville (1969) observed no significant difference between the performance of Type V sulfate resisting and Type I (C₃A content of 9%) cements upon exposure of concrete specimens to both weak and saturated MgSO₄ solutions. Previous research also observed no significant difference between the performance of ASTM Type I and Type V cements when both were exposed to a marine environment (Gjorv and Vennesland, 1979). About 8% C₃A is typically needed to consume the gypsum that is invariably added to regulate the time of set during the early hydration of cement (Mehta, 1981). Consequently, for the Type I Portland cement used in this study, only 0.1% C₃A would remain to react with sulfates, which is unlikely to cause extensive damage. Kalousek et al. (1972) confirms that limitations on C₃A and C₄AF contents are not the ultimate answer to the problem of sulfate attack. This situation may also be explained from the mechanisms of sodium sulfate and magnesium sulfate attack as summarized in the following equations (Mather, 1968):








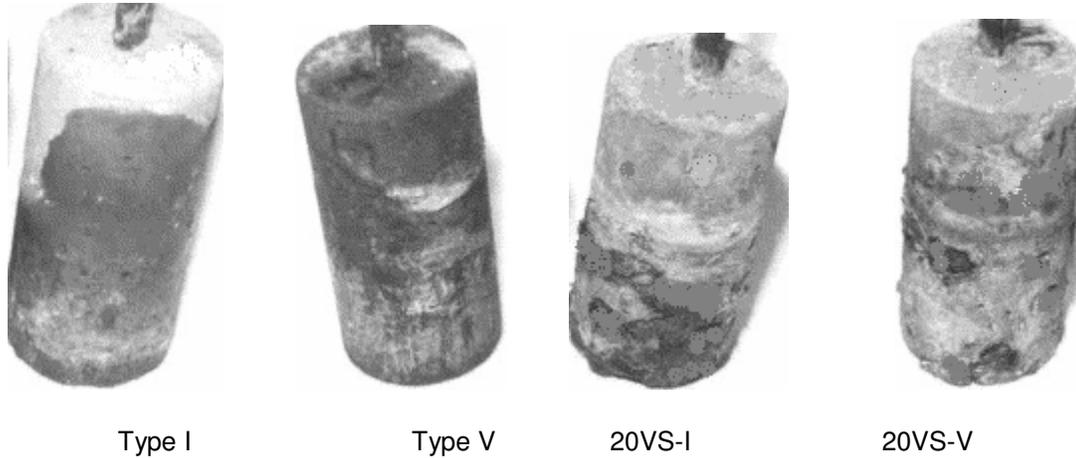


Figure 8. Typical deterioration after 48 months of exposure (W/B = 0.45)



where C = CaO, N = Na₂O, M = MgO, S = SO₃, Si = SiO₂, H = H₂O

In sodium sulfate (NS) environment, NS reacts with calcium hydroxide (CH) to form calcium sulfate (gypsum, CSH₂) as per Eq. 3. This reaction may eventually continue to completion, i.e., leaching of all CH. Calcium sulfate formed can subsequently react with C₃A, usually via the formation of monosulfoaluminate, to form ettringite (C₆AS₃H₃₂) as per Eq. 7. It is to minimize the reaction with C₃A that Type V cement was developed. In magnesium sulfate (MS) environment, MS reacts with all products of hydration of cement; the important resulting compounds are calcium sulfate and brucite (MH) as in Eq. 4. Calcium sulfate can proceed to react with C₃A to form ettringite, eventually. Specifically, in the case of sodium sulfate, the use of cement with a low C₃A content mini-

mizes the extent of reaction with sodium sulfate and, therefore, of the formation of ettringite.

In mixed sulfate environment, the mode of sulfate attack is predominantly controlled by MS due to generation of brucite (MH) as in Eq. 4. Brucite being insoluble (its solubility is 0.01 g/l compared to 1.37 g/l for CH) and its saturated solution having a pH of about 10.5, causes the destabilization of both ettringite and calcium silicate hydrate (C-S-H). The formation of secondary ettringite is significantly hindered in such environments. C-S-H decomposes, liberating CH. This CH reacts with MS and forms further brucite and gypsum. This reaction continues until gypsum is crystallized out (Rasheeduzzafar et al., 1994). Brucite reacts also with silicate hydrate arising from the decomposition of C-S-H, and results in the formation of magnesium silicate hydrate, which lacks cohesive properties. These reactions take place even when the C₃A content in the cement is very low (Rasheeduzzafar et al., 1994). Accordingly, this type of sulfate attack is typically characterized by a deterioration akin to eating away of hydrated cement mortar/paste and progressively reducing it to a cohesionless granular mass that may expose the aggregate in case of concrete associate with loss of strength. This type of sulfate attack is mainly attributed to the formation of gypsum as in Equations 3 and 4. Since ettringite ceases to be a deteriorating parameter in mixed sulfate environments, the role of C₃A content in sulfate attack (Eqs. 5 to 7) will not be effective. Accordingly, sulfate attack in plain cements will be initiated by Eqs. 3 and 4 and will proceed directly to Eqs. 8 and 9. These reactions (Eqs. 3, 4, 8 and 9) do not involve any aluminate phase in the deterioration mechanisms and, therefore, the ettringite formation will practically be inhibited. Consequently, the influence of C₃A content on the sulfate attack in mixed sulfate environments does not appear to be crucial as is the case in Na₂SO₄ environments.

Although two types of Portland cements with a C₃A content varying in the range of 3.5 (Type V) to 8.5% (Ty-

pe I), the results of weight loss, corrosion potential and polarization resistance show that the sulfate attack is not totally or predominantly controlled by the C_3A content.

Influence of W/B

A reduction in the W/B from 0.45 to 0.35 enhanced the weight loss of both Type I and V plain cement concrete mixtures. Type I and Type V plain concrete mixes with W/B of 0.45 had a weight loss of 1.34 and 1.51%, respectively after an exposure period of 48 months compared with 5.7 and 3.3% for the same concrete mixtures with W/B of 0.35 (Table 6). Such deleterious effect of lower W/B is also reported from other research studies (Kalousek et al., 1972; Al-Amoudi, 2002; Mehta, 1981). A likely explanation is that at low W/B, there is limited pore space to accommodate the products of reaction with sulfate namely, magnesium silicate hydrate (which has no adhesive properties) and gypsum. However, Kalousek et al. (1972) stated that actual effect of high W/B on sulfate resistance is not clearly understood.

Despite the higher degree of sulfate deterioration in low W/B concrete mixtures (W/B = 0.35), the low negative corrosion potentials and high polarization resistance values reveal that their embedded reinforcing steel was still in a passive state compared with those of high W/B of 0.45 after 48 months of immersion (Table 6). This can be attributed to the fact that the initiation of corrosion in embedded steel is not only a function of concrete deterioration.

Influence of VS on sulfate resistance

Concrete specimens with W/B of 0.45 exhibited an increase in weight loss from 1.34% (Type I plain cement) to 16.9% (Type I VS blended cements) within the 48 month of immersion period (Table 6). An increase in weight loss from 5.7% (Type I plain cement) to 12.6% (Type I VS blended cements) was observed in specimens with a W/B of 0.35. Concrete specimens with W/B of 0.45 exhibited an increase in weight loss from 1.5% (Type V plain cement) to 12.2% (Type V VS blended cements). An increase in weight loss from 3.3% (Type V plain cement) to 8.3% (Type V VS blended cements) was observed in specimens with a W/B of 0.35. Type I/V VS based blended cement concrete specimens showed higher and faster rate of deterioration than those of Type I/V plain cement concrete specimens. Similar faster rate of deterioration was observed in specimens with fly ash, silica fume and slag blended cements in magnesium-based sulfate environment (Mangat and El-Khatib, 1992; Cohen and Bentur, 1988; Bonen, 1993). The higher deterioration in Type I and Type V VS based blended cement concretes in sulfate environment compared to Type I and Type V plain Portland cement concretes can be attributed

to the presence of Mg^{2+} cations associated with $MgSO_4$. The consumption of portlandite ($Ca(OH)_2$) by the pozzolanic reaction in VS blended cements causes Mg^{2+} cations to react directly with the calcium silicate hydrate (C-S-H) gel converting it to cohesionless, porous, reticulated magnesium silicate hydrate (M-S-H) gel as illustrated in Eqs. 8 and 9.

The consumption of $Ca(OH)_2$ by pozzolanic reaction is evidenced by the presence of lower quantity of $Ca(OH)_2$ in Type I/V VS based blended cement concrete compared to Type I and Type V plain cement concrete without exposure to sulfate environment (at 56 days) and after exposure to sulfate environment for 48 months (Table 5 based on DSC analysis).

It is also noted that the Type I/V VS based blended cement concrete specimens exhibited weight loss which were more than the 2.5% failure criterion (Table 6). Use of Type V cements reduced the deterioration of VS based concrete specimens compared with those of Type I possibly due to lower C_3A content.

The type I/V VS based blended cement concretes showed inferior performance compared with Type I/V plain cement concretes in terms of corrosion resistance at 48 month of immersion. This could be attributed to the advance stage of deteriorations (in Type I/V VS based blended concretes) at this period whereby a weight loss that ranged between 8.3 and 16.9 (Table 6) which is higher than 2.5% was observed. High degree of deterioration in blended cement concrete mixtures could not preserve the integrity of the internal structure and enabled the SO_4 ions to diffuse to the steel, leading to corrosion of reinforcing steel. On the contrary, the specimens made with plain Type I/V cements exhibited better resistance to sulfate attack, especially specimens with W/B of 0.35 where reinforcing steels were not found to be in active state of corrosion (polarization resistance > 87 $k\Omega\text{-cm}^2$) after 48 months of exposure. This might be attributed to the mechanism of $MgSO_4$ attack as well as to the diffusion of SO_4^{2-} ions.

CONCLUSIONS

The deterioration and corrosion resistance of finely ground volcanic scoria (VS) based Type I and Type V blended cement concretes in mixed magnesium-sodium sulfate environment for an immersion period of 48 months are evaluated through physico-chemical deterioration of concrete and electro-chemical behaviour of embedded steel. The influence of type of cement (ASTM Type I or V to be used in VS based blended cements) and water-to-binder ratio on sulfate resistance is also studied. The following conclusions are drawn from the study:

Type I/V VS based blended cement concrete mixtures exhibited an advanced stage of deterioration (poor performance) when compared to Type I/Type V plain cement

concrete mixtures after 48 months of immersion in mixed sulfate environment. This can be attributed to the consumption of portlandite by the pozzolanic reaction in VS blended cements that causes Mg^{2+} cations to react directly with C-S-H gel converting it to cohesionless, porous, reticulated M-S-H gel.

Use of Type V cements reduced the deterioration of VS based blended concrete specimens compared with those of Type I. However, Type I/V VS based blended cement concrete specimens exhibited weight loss which were more than the 2.5% failure criterion.

A reduction in the W/B from 0.45 to 0.35 enhanced the weight loss (deterioration) of both Type I and V plain cement concrete mixtures possibly due to the limited pore space to accommodate the products of reaction with sulfate. However, a decrease in W/B from 0.45 to 0.35, decreases the weight loss of Type I/V VS based cement concretes.

Type I/V VS based blended cement concrete mixtures showed inferior performance compared with Type I/V plain cements in terms of corrosion resistance after 48 months. Specimens made with plain Type I/V cements exhibited better resistance to sulfate attack, especially specimens with W/B of 0.35 where reinforcing steels were not found to be in active state of corrosion after 48 months of exposure.

The results presented in this study will provide assistance to the readers in understanding the performance of Type I/V VS based blended cement concretes in mixed sulfate environment.

ACKNOWLEDGEMENT

The author is grateful to the Papua New Guinea (PNG) Halla Cement Factory, PNG Department of Works, Gazella Restoration Authority of Rabaul (PNG) and PNG Ready Mixed Concrete Co. Ltd. for their support.

REFERENCES

- ACI committee 201 (1991). Proposed revision of: Guide to durable concrete, *ACI Mater. J.* 88 (2):544-582.
- Al-Amoudi OSB (2002). Attack on plain and blended cements exposed to aggressive sulfate environments, *Cem. Concr. Compos.* 24 (3 – 4): 305– 316.
- Al-Amoudi OSB, Abduljawwad SN, Rasheeduzzafar FA, Maslehuddin RM (1992). Effect of chloride and sulfate contamination in soils on corrosion of steel and concrete, *Transport. Res. Rec.* 1345: 67-73.
- Al-Amoudi OSB, Maslehuddin RM, Abduljawwad SN (1994). Influence of chloride ions on sulphate deterioration in plain and blended cements, *Mag. Concr. Res.* 46(167): 113-123.
- Andrade C, Castelo V, Alonso C, Gonzalez JA (1986). The determination of corrosion rate of steel embedded in concrete by the polarization resistance and AC impedance methods, In *Proc. ASTM STP 906*, ASTM, Philadelphia. pp: 43-63.
- Bonen DA (1993). A microstructural study of the effect produced by magnesium sulfate on plain and silica fume –bearing Portland cement mortars, *Cem. Concr. Res.* 23(3): 541-553.
- Broomfield JP, Langford PE, Ewins AJ (1990). In: Berke NS, Chaker V, Whiting D (Eds.), *Corrosion rates of steel in concrete*, ASTM STP 1065, Philadelphia, USA. pp: 157.
- Cohen MD, Bentur A (1988). Durability of Portland silica fume pastes in magnesium and sodium sulfate solutions, *ACI Mater. J.* 85(3): 148-157.
- Cohen MD, Mather B (1991). Sulphate attack on concrete - research needs, *ACI Mat. J.* 88(1): 62-69.
- Frigione G, Sersale R (1989). The action of some aggressive solutions on Portland, pozzolanic and blast furnace slag cement mortars. *Cem. Concr. Res.* 19(6): 885- 893.
- Gjorv OE, Vennesland O (1979). Diffusion of chloride ions from sea water concrete. *Cem. Concr. Res.* 9(2): 229-238.
- Hossain KMA (2004). Properties of volcanic scoria based lightweight concrete. *Mag. Concr. Res.* 56(2): 111-120.
- Hossain KMA (2006). Blended cement and lightweight concrete using scoria: mix design, strength, durability and heat insulation characteristics, *Int. J. Phys. Sci.* 1(1): 5-16.
- Irrassar EF, Gonzalez M, Rahhal V (2000). Sulphate resistance of Type V cements with limestone filler and natural pozzolana. *Cem. Concr. Compos.* 22(5): 361–368.
- Kalousek GL, Porter LC, Benton EJ (1972). Concrete for long-time service in sulfate environment. *Cem. Concr. Res.* 2(1): 79- 89.
- Lawrence CD (1990). Sulphate attack on concrete, *Mag. Concr. Res.* 42 (153): 249- 264.
- Mangat PS, El-Khatib JM (1992). Influence of initial curing on sulphate resistance of blended cement concrete, *Cem. Concr. Res.* 22(6): 1089-1100.
- Mather M (1968). Field and laboratory studies of the sulphate resistance of concrete, In *Performance of Concrete*, ed. Swenson E.G., University of Toronto Press. pp: 66-76.
- Mehta PK (1973). Mechanisms of expansion associated with ettringite formation, *Cem. Concr. Res.* 3(1): 1-6.
- Mehta PK (1981). Effect of cement composition on corrosion of reinforcing steel in concrete, *Chloride corrosion of steel in concrete*. ASTM STP 629, Philadelphia. pp: 12-19.
- Mehta PK (1993). Sulfate attack on concrete: a critical review, *Materials Science of Concrete*, Ohio. Am. Ceram. Soc. Vol. 3: 105–130.
- Montemor MF, Simoes AMP, Salta MM (2000). Effect of fly ash on concrete reinforcement corrosion studied by EIS. *Cem. Concr. Compos.* 22(2): 175-185.
- Neville A (1969). Behaviour of concrete in saturated and weak solutions of magnesium sulphate or calcium chloride. *J. Mater. ASTM*, 4(4): 781-816.
- Neville A (2004). The confused world of sulfate attack on concrete. *Cem. Concr. Res.* 34(8): 1275-1296.
- Rasheeduzzafar, Al-Amoudi OSB, Abduljawwad SN, Maslehuddin M (1994). Magnesium – sodium sulfate attack in plain and blended cements, *ASCE J. Mater. Civ. Eng.* 6(2): 201– 222.
- Rasheeduzzafar, Dakhil FA, Al-Gahtani AS, Al-Saadoun SS, Bader MA (1990). Influence of cement composition on the corrosion of reinforcement and sulfate resistance of concrete, *ACI Mater. J.* 87(2): 114-122.
- Taylor HFW (1999). Discussion, *Sulfate Attack Mechanisms*, Materials Science of Concrete Special Volume, Ohio. Am. Ceram. Soc. pp: 33– 34.
- Washburn EW (1921). Note on a method of determining the distribution of pore sizes in a porous materials, USA. *Proc. Natl. Acad. Sc.* 7: 115-116.
- Wong G, Poole T (1987). Effect of pozzolans and slags on the sulfate resistance of hydraulic cement mortars, *Concrete Durability*, ACI, Detroit. ACI SP-100: 100-109.
- Young JF, Mindess S, Gray RJ, Bentur A (1998). *The Science and Technology of Civil Engineering Materials*, Prentice-Hall, New Jersey.